



Terahertz time-domain spectroscopy of transient metallic and superconducting states

J. Orenstein^{1,2,*} and J. S. Dodge^{3,4,†}

¹*Department of Physics, University of California, Berkeley, California 94720, USA*

²*Materials Science Division, Lawrence Berkeley National Laboratory, Berkeley, California 94720, USA*

³*Department of Physics, Simon Fraser University, Burnaby, British Columbia, Canada V5A 1S6*

⁴*Canadian Institute for Advanced Research, Toronto, Ontario, Canada M5G 1Z8*

(Received 24 June 2015; revised manuscript received 31 August 2015; published 9 October 2015)

Time-resolved terahertz time-domain spectroscopy (THz-TDS) is an ideal tool for probing photoinduced nonequilibrium metallic and superconducting states. Here, we focus on the interpretation of the two-dimensional response function $\Sigma(\omega; t)$ that it measures, examining whether it provides an accurate snapshot of the instantaneous optical conductivity $\sigma(\omega; t)$. For the Drude model with a time-dependent carrier density, we show that $\Sigma(\omega; t)$ is not simply related to $\sigma(\omega; t)$. The difference in the two response functions is most pronounced when the momentum relaxation rate of photocarriers is small, as would be the case in a system that becomes superconducting following pulsed photoexcitation. From the analysis of our model, we identify signatures of photoinduced superconductivity that could be seen by time-resolved THz-TDS.

DOI: 10.1103/PhysRevB.92.134507

PACS number(s): 78.47.-p, 78.56.-a, 42.65.-k, 74.25.N-

I. INTRODUCTION

Time-domain terahertz spectroscopy (THz-TDS) probes the optical conductivity of metals and superconductors by measuring the current transient induced by a subpicosecond electric field pulse. Time-resolved THz-TDS exploits the short duration of the THz probe to detect how the conductivity changes in response to pulsed photoexcitation after a controlled delay—providing a way to take snapshots of the optical conductivity with picosecond time resolution. This scheme has been used effectively to measure transient photoconductivity in a wide variety of bulk and nanostructured semiconductor systems [1], and its range of application is growing [2–4]. Recently, THz-TDS spectra of the photoexcited normal state of high- T_c cuprates and K_3C_{60} have been presented as evidence of transient photoinduced superconductivity, because they resemble the equilibrium conductivity spectra obtained well below the superconducting transition temperature [5–8]. However, the straightforward interpretation of THz-TDS as a snapshot of the optical conductivity spectrum breaks down when the characteristic relaxation times are comparable to the photoexcitation delay, because the Fourier transform involves times that precede photoexcitation [1,9–16].

In order to assess the importance of this issue for interpreting measurements on transient metallic and superconducting states, we analyze a simple model of transient photoconductivity [12–15]. For photoexcitation at $t = 0$, we compare the time-dependent instantaneous conductivity change $\delta\sigma(\omega; t)$ with the response function $\Sigma(\omega; t)$ measured in time-resolved THz-TDS. We find that Σ shows large-amplitude deviations from $\delta\sigma$ when the photocarrier Drude scattering time is longer than t [14], a regime that may be accessible in a transient photoinduced superconductor. Our analysis offers improved guidance on how and when time-resolved THz-TDS spectra can be interpreted as a conductivity snapshot of a transient state.

We consider a pump-probe experiment in which a material is photoexcited by a strong pump pulse with intensity profile $I(t) \approx I_0\delta(t)$, and the current induced by a THz-frequency probe field is measured at time t . The photoinduced change in the current is then

$$\delta J(t) = \iint_{-\infty}^{\infty} E(t - \tau)I(t - \tau_e)\sigma^{(3)}(\tau, \tau_e)d\tau d\tau_e, \quad (1)$$

where $E(t - \tau)$ is the electric field of the THz probe at the moment τ before the observation time, and $\sigma^{(3)}(\tau, \tau_e)$ is a third-order susceptibility, in the sense that its associated current is proportional to both the THz probe field and the pump intensity (two powers of field). By defining

$$\Sigma(\tau, t) = \int_{-\infty}^{\infty} I(t - \tau_e)\sigma^{(3)}(\tau, \tau_e)d\tau_e, \quad (2)$$

we can rewrite Eq. (1) as

$$\delta J(t) = \int_{-\infty}^{\infty} E(t - \tau)\Sigma(\tau, t)d\tau, \quad (3)$$

which has the usual linear response form—except, crucially, that the two-dimensional response function $\Sigma(\tau, t)$ has an implicit dependence on $I(t)$ and lacks time invariance [9–11]. Kindt and Schmuttenmaer (KS) pointed out that $\Sigma(\tau, t)$ could be readily obtained with time-resolved THz-TDS by independently controlling the delay of the THz probe field with respect to photoexcitation, as illustrated in Fig. 1 and described more thoroughly in Sec. III [17].

With a measurement of $\Sigma(\tau, t)$, it is straightforward to compute the Fourier transform $\Sigma(\omega; t)$. The question that arises then is the following: whether, or in what limit, can $\Sigma(\omega; t)$ be considered equivalent to the pump-induced change in the instantaneous optical conductivity, $\delta\sigma(\omega; t)$ [1,9–16]? Indeed, whether the response function $\delta\sigma(\omega; t)$ exists at all for an arbitrary nonequilibrium system is itself a problem, one we do not consider here. Instead, we consider a specific example of a class of optically pumped systems for which the concept of an instantaneous linear response function should be applicable. Following photoexcitation, this class of systems passes through a continuous sequence of

*jworenstein@lbl.gov

†jsdodge@sfsu.ca

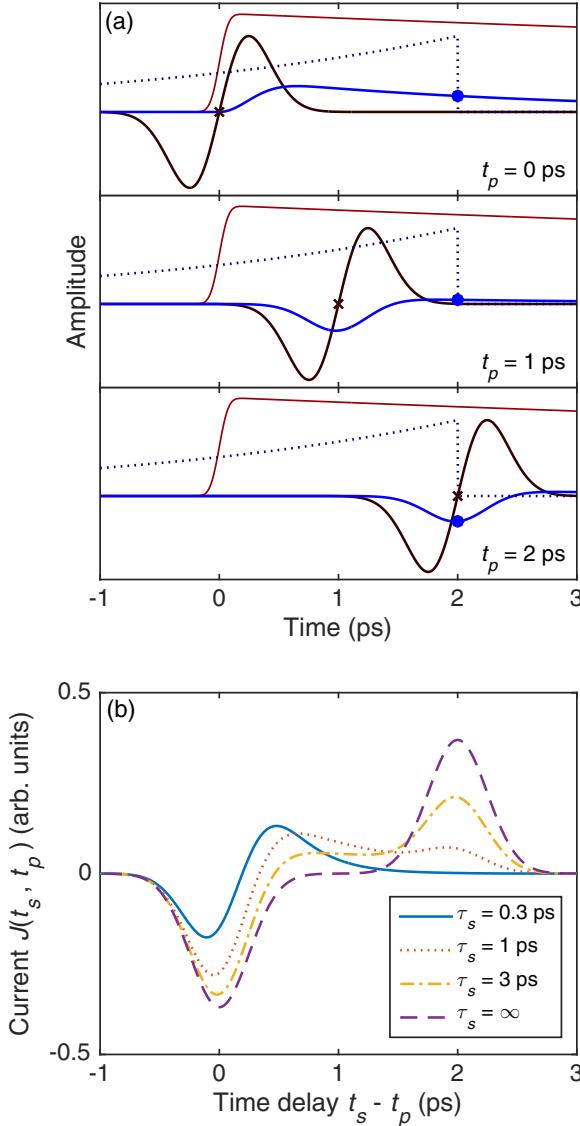


FIG. 1. (Color online) (a) Schematic illustration of the pulse sequence and time delays in a time-resolved THz-TDS measurement performed on the model system described in the text. The red lines represent the photoexcited carrier density that is generated by a pump pulse at $t = 0$ and then decays on a time scale of $1/\Gamma = 20 \text{ ps}$. The black lines represent the electric field of the THz probe pulse, shown for increasing time delay, t_p (marked by \times), in the three panels. The blue lines depict the corresponding nonequilibrium current, and the blue dots mark its value at $t_s = 2 \text{ ps}$. The dotted line shows the impulse response function $\sigma(t_s - t)$ for a Drude metal. The truncation of the impulse response at $t = 0$ differentiates $\Sigma(\tau, t_s)$ from $\delta\sigma(\tau, t_s)$. (b) Nonequilibrium current as a function of $t_s - t_p$ for fixed $t_s = 2 \text{ ps}$ and $1/\Gamma = 20 \text{ ps}$. With increasing momentum relaxation time, τ_s , a pulse of nonequilibrium current centered on $t_p = 0$ grows in amplitude.

quasiequilibrium states, in which the distribution functions of electrons, phonons, magnons, etc., can be described by quasitemperatures and effective chemical potentials. For such systems it should be possible to define the response function $\delta\sigma(\omega; t)$ as the change in the equilibrium $\sigma(\omega)$ that would be measured if the quasiequilibrium state at time t were entirely

metastable. Below we show by example that although $\delta\sigma(\omega; t)$ can be well defined, it is not, in general, equivalent to the function $\Sigma(\omega; t)$ measured by time-resolved THz-TDS.

II. EXAMPLE OF PHOTOCARRIERS WITH DRUDE RESPONSE

We treat the Drude model for nonequilibrium photocarriers, but it is helpful to start with elementary equilibrium relationships. For a system of n carriers with Drude scattering rate γ , the current is given by

$$J(t) = \int_{-\infty}^{\infty} E(t - \tau)\sigma(\tau)d\tau, \quad (4)$$

with the impulse response

$$\sigma(\tau) = \frac{ne^2}{m}\Theta(\tau)\exp(-\gamma\tau). \quad (5)$$

The Drude conductivity spectrum is then just the Fourier transform of Eq. (5):

$$\sigma(\omega) = \frac{ne^2}{m} \frac{1}{\gamma - i\omega}. \quad (6)$$

We turn now to the nonequilibrium case. If photoexcitation creates $\delta n(0)$ carriers that recombine at a rate Γ , then the instantaneous conductivity is given by the Drude formula with $n(t) = \delta n(0)\Theta(t)\exp(-\Gamma t)$,

$$\delta\sigma(\omega; t) = \Theta(t) \frac{\delta n(0)e^2}{m} \exp(-\Gamma t) \frac{1}{\gamma - i\omega}, \quad (7)$$

or, in the time domain,

$$\delta\sigma(\tau, t) = \Theta(t) \frac{\delta n(0)e^2}{m} \exp(-\Gamma t)\Theta(\tau)\exp(-\gamma\tau). \quad (8)$$

We emphasize here that in both $\delta\sigma(\tau, t)$ and $\delta\sigma(\omega; t)$, the dependence on t is entirely through the state variable $n(t)$, which is then assumed to be constant when we consider the dependence of $\delta\sigma$ on the dynamical variables τ and ω .

By contrast, $\Sigma(\tau, t)$ has an explicit dynamical dependence on t . Because of the relative simplicity of our model, we can determine $\Sigma(\tau, t)$ directly by integrating the classical equation of motion for the photocarriers. As shown in the Appendix, we obtain [12]

$$\Sigma(\tau, t) = \Theta(t - \tau)\Theta(t) \frac{\delta n(0)e^2}{m} \exp(-\Gamma t)\Theta(\tau)\exp(-\gamma\tau). \quad (9)$$

Equation (9) is identical to Eq. (8) except for the additional Heaviside function, $\Theta(t - \tau)$, which prevents carriers from contributing to the integrand in Eq. (3) before they are created at $t = 0$ (or $\tau = t$).

Substituting this form for $\Sigma(\tau, t)$ into Eq. (3) yields

$$\delta J(t) = \Theta(t) \frac{\delta n(0)e^2}{m} \exp(-\Gamma t) \times \int_{-\infty}^{\infty} E(t - \tau)\Theta(t - \tau)\Theta(\tau)\exp(-\gamma\tau). \quad (10)$$

In the following section we show how time-resolved THz-TDS is applied to measure $\Sigma(\tau, t)$, and we compare $\Sigma(\omega; t)$ with $\delta\sigma(\omega; t)$.

III. TIME-RESOLVED TERAHERTZ SPECTROSCOPY

As a preliminary step we review the methodology of THz-TDS as applied to the equilibrium optical conductivity [1]. THz-TDS effectively measures the current at the sampling time t_s that is induced by a THz electric field pulse, $E(t) = E_p(t - t_p)$, centered on the probe arrival time t_p :

$$\hat{J}(t_s, t_p) = \int_{-\infty}^{\infty} E_p(t_s - t_p - \tau) \sigma(\tau) d\tau. \quad (11)$$

The induced current $\hat{J}(t_s, t_p)$ is inferred from a time-resolved measurement of the electric field reflected from, or transmitted through, a medium under test. It depends only on the difference $t_s - t_p$ between the sampling and probe arrival times, so it can be measured by scanning either t_s or t_p . Using the convolution theorem, $\sigma(\omega)$ can be obtained by Fourier transforming $\hat{J}(t_s, t_p)$ along the $\Delta t = t_s - t_p$ direction.

Time-resolved THz-TDS focuses on the change in the response to the THz probe that is induced by a pump pulse. The sequencing of pump and THz probe pulses is illustrated in Fig. 1(a). Using Eq. (10), the nonequilibrium current for Drude photocarriers is

$$\delta \hat{J}(t_s, t_p) = \Theta(t_s) \frac{\delta n(0)e^2}{m} \exp(-\Gamma t_s) \int_{-\infty}^{\infty} E_p(t_s - t_p - \tau) \times \Theta(t_s - \tau) \Theta(\tau) \exp(-\gamma \tau) d\tau. \quad (12)$$

Note that $\delta \hat{J}(t_s, t_p)$ is now a function of both the sampling time and the probe arrival time, rather than just their difference, as in equilibrium THz-TDS; this reflects the breaking of time invariance by the pump. An example of the transient nonequilibrium current calculated from Eq. (12) is illustrated in Fig. 1(b), which shows $\delta \hat{J}(t_s, t_p)$ as a function of $t_s - t_p$ with $t_s = 2$ ps, for several values of $\tau_s \equiv 1/\gamma$. For $\tau_s = 0.3$ ps, the current follows the electric field pulse, with a lag and slight distortion caused by convolution with the Drude impulse response. As τ_s increases, a feature emerges near $t_p = 0$ that has a completely different origin, illustrated in the $t_p = 0$ panel of Fig. 1(a): here, only part of the THz field can induce current, creating an unbalanced current impulse that persists until the measurement time t_s . When $\tau_s \rightarrow \infty$, as in a superconductor, these two features have equal and opposite magnitude; however, their separation in time will vary with the observation time t_s .

The procedure introduced by KS is to scan t_p at fixed t_s , such that the integral expression for the current retains the form of Eq. (11), but with the two-dimensional nonequilibrium response function $\Sigma(\tau, t_s)$ in place of $\sigma(\tau)$, as in Eq. (3). If we now Fourier transform $\Sigma(\tau, t_s)$ with respect to τ , we get

$$\Sigma(\omega; t_s) = \Theta(t_s) \frac{\delta n(0)e^2}{m} \exp(-\Gamma t_s) \frac{1}{\gamma - i\omega} \times [1 - \exp(-\gamma t_s) \exp(i\omega t_s)], \quad (13)$$

which differs from the instantaneous conductivity $\delta\sigma(\omega; t_s)$ in Eq. (8) by the term in square brackets. This result is consistent with earlier results on the nonequilibrium Drude model [11–15], expressed in a way that allows more immediate comparison with experiment.

While we have focused on the nonequilibrium current $\delta \hat{J}(t_s, t_p)$ for generality, experimental methods to determine

it vary [1]. For transmission through a weakly absorbing, thin medium, the current density and probe fields are essentially independent of depth, in which case $\delta \hat{J}(t_s, t_p)$ can be inferred directly from the transmitted field. For reflection from a thick absorbing material, the depth scale of the photoexcited and probed regions of the sample may differ; typically the decay length of the probe is greater. Taking into account the spatially varying conductivity of the probed region requires careful consideration (see, for example, the supplementary section of Ref. [8]). In both cases, the electrooptic detection process filters the reflected or transmitted field, which also distorts $\delta \hat{J}(t_s, t_p)$; but since $E_p(t_s - t_p)$ is measured in the same way, deconvolution yields an undistorted $\Sigma(\omega; t_s)$ [18–20].

We have also assumed impulsive excitation, $I(t) \approx I_0 \delta(t)$, that causes the conductivity to change abruptly. When the excitation pulse width τ_w cannot be neglected, we expect the oscillations in $\Sigma(\omega; t_s)$ to become damped as $\omega \tau_w \gtrsim 1$. Another factor that can lead to damping occurs if the photoinduced change in conductivity has a finite rise time. This would be reflected in the dependence of the third-order susceptibility $\sigma^{(3)}(\tau, \tau_e)$ on τ_e in Eq. (2). In the presence of either form of broadening of the step-function change in conductivity, the deviation of Σ from σ will be most pronounced at low frequencies, which is indeed observed [9,21].

IV. DISCUSSION

Equation (13) greatly clarifies the conditions under which the time-resolved THz-TDS spectrum $\Sigma(\omega; t_s)$ approximates the instantaneous linear response $\delta\sigma(\omega; t_s)$. First, it shows that photocarrier recombination simply rescales the overall spectrum by $\exp(-\Gamma t_s)$, so the measurement fidelity is not fundamentally limited by the recombination time. The critical parameter is γt_s , the product of the momentum relaxation rate and the sampling time. The crossover in the nature of the spectra at $\gamma t_s \sim 1$ is illustrated in Fig. 2(a), in which we plot $\Sigma(\omega; t_s)$ as a function of ω for several values of τ_s , with t_s fixed at 2 ps. The instantaneous Drude conductivity $\delta\sigma(\omega; t_s)$ for the same values of τ_s is shown as dotted lines for comparison, and spectra with different τ_s are normalized to $\delta\sigma(\omega; t_s = 0)$ to illustrate the variation in frequency dependence.

When t_s/τ_s is large, the component of the current sampled at t_s from carriers accelerated at $t = 0$ is exponentially small. Consequently, $\Sigma(\omega; t_s)$ asymptotically approaches the instantaneous conductivity, which has the Drude form in our simple example. On the other hand, if τ_s is comparable to or greater than t_s , a component of the current that would be present if the state were metastable is cut off at $t = 0$. The temporal cutoff generates oscillations with period $\Delta\omega = 2\pi/t_s$ along the frequency axis of $\Sigma(\omega; t_s)$, which is clearly no longer simply related to $\delta\sigma(\omega; t_s)$.

Figure 3 shows this behavior in more detail as it would appear for photocarriers with $\tau_s = 1$ ps and $1/\Gamma = 0.5$ ps. The imaginary part of $\Sigma(\omega; t_s)$ has oscillations that appear as ridges along constant values of ωt_s , with an amplitude that decays exponentially with γt_s . Similar oscillations were observed previously in both measurements [21] and simulations [14], and Eq. (13) clarifies their origin.

Finally, we consider what might be observed in a time-resolved THz-TDS measurement in which a transient su-

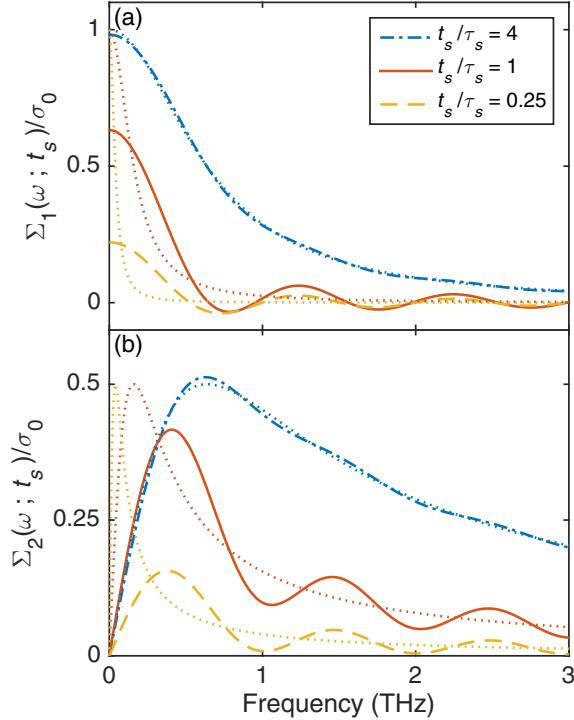


FIG. 2. (Color online) (a) Real and (b) imaginary parts of $\Sigma(\omega; t_s)$ as a function of ω for several values of τ_s , with t_s fixed at 1 ps and $\Gamma = 0$. The Drude conductivity for the same values of τ_s is shown as dotted lines for comparison. Spectra with different τ_s are normalized to $\sigma_0 = n(0)\tau_s e^2/m$ to illustrate the variation in frequency dependence. When t_s/τ_s is large, $\Sigma(\omega; t_s)$ asymptotically approaches the instantaneous (Drude) conductivity. For $\tau_s \geq t_s$ the temporal cutoff at $t = 0$ generates oscillations, with period $\Delta\nu = 1/t_s$ along the frequency axis of $\Sigma(\omega; t_s)$.

perconducting phase is generated at $t = 0$ by a laser pulse. Developing a phenomenological description of transient superconductivity is clearly not as straightforward as modeling a transient photoconductor. One approach that is directly amenable to our analysis is based on the two-fluid model, which describes the current response in terms of normal fluid and superfluid components, with spectral weights $n_n e^2/m$ and $n_s e^2/m$, respectively. The normal fluid conductivity is described by the Drude spectrum, while the superfluid component is characterized by an infinite momentum relaxation time. We can then formulate photoinduced superconductivity as the generation of superfluid spectral weight $\Delta n e^2/m$ by transfer from the normal fluid. If we assume that the photoinduced superfluid has a lifetime $1/\Gamma$, then

$$\Sigma(\omega; t_s) = i\Theta(t_s) \frac{\Delta n e^2}{m} \exp(-\Gamma t_s) \times \left\{ \frac{1}{\omega} [1 - \exp(i\omega t_s)] - \frac{1}{\tilde{\omega}} [1 - \exp(i\tilde{\omega} t_s)] \right\}, \quad (14)$$

with $\tilde{\omega} \equiv \omega + i\gamma$. Figure 4 illustrates the spectra predicted by Eq. (14) for several values of t_s , with $\tau_s = 1$ ps and $\tau_r = 0.5$ ps. The spectral shape is dominated by underdamped oscillations that originate from the sharp cutoff in the time-

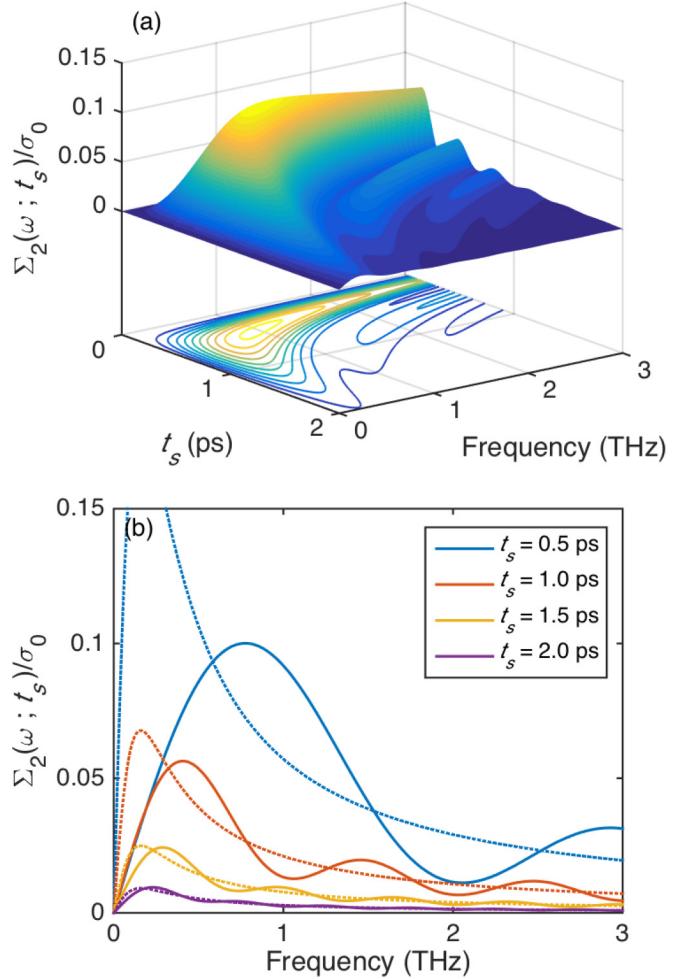


FIG. 3. (Color online) Simulation of time-resolved THz-TDS response function for photocarriers whose dynamics are characterized by a time-independent scattering rate. (a) Imaginary part of $\Sigma(\omega; t_s)$, with $\tau_s = 1$ ps and $1/\Gamma = 0.5$ ps, in both three-dimensional and contour plot representations. Contour levels indicate 0.01 steps from 0.01 to 0.1, inclusive. (b) Spectra of $\Sigma_2(\omega; t_s)$ (solid lines) for several values of t_s , with $\delta\sigma_2(\omega; t_s)$ (dotted lines) shown for comparison. The spectrum for each t_s is denoted by color in the legend; both Σ_2 and σ_2 decrease with increasing t_s , as the carriers decay. All spectra are normalized to $\sigma_0 \equiv \delta n(0)e^2\tau_s/m$.

domain response at $t = 0$, as discussed above. We note that in this description of transient superfluidity, $\Sigma(\omega; t_s)$ never approaches $\delta\sigma(\omega; t_s)$ because of the undamped contribution to $\hat{J}(t_s, t_p)$ from supercarriers generated at $t = 0$. With an overall sign change, Eq. (14) should also describe $\Sigma(\omega; t_s)$ when photoexcitation suppresses superconductivity, for example, by transferring spectral weight from the superconducting carriers to quasiparticles above the gap [9].

We note that the oscillations that appear in our simulations are distinct from oscillations in the time domain that appear often in time-resolved spectroscopic probes, where their presence reflects a sharp feature in the frequency domain, like a plasma reflectivity edge. Here, the domains are reversed: the time-domain cutoff imposed by causality creates oscillations in the frequency domain. Unlike time-domain oscillations, whose frequency corresponds to excited state energies, the frequency

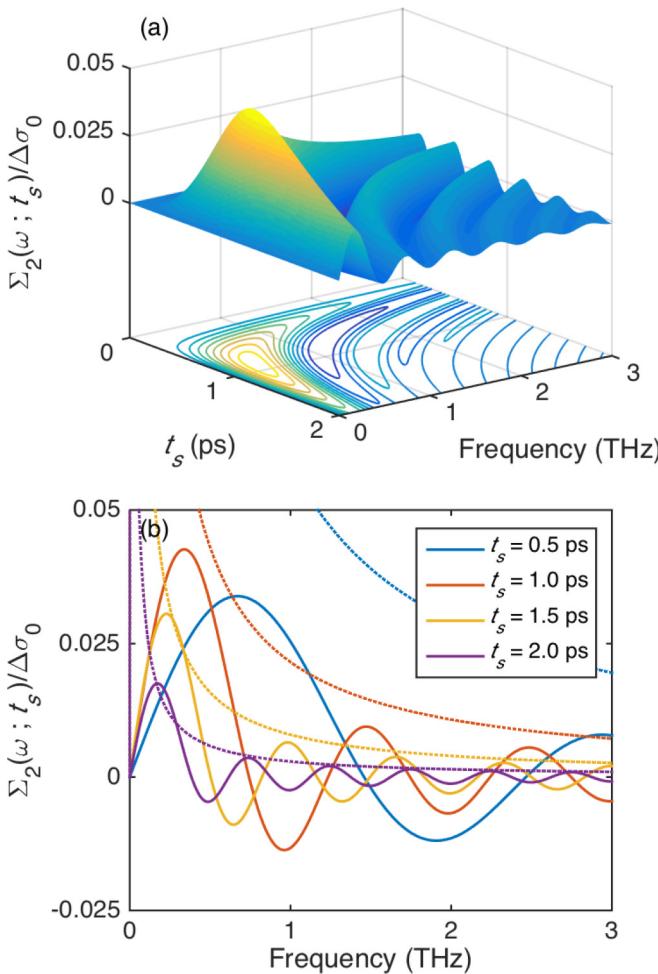


FIG. 4. (Color online) Simulation of time-resolved THz-TDS response function for a model of transient photoinduced superconductivity. (a) Imaginary part of $\Sigma(\omega; t_s)$, with $\tau_s = 1$ ps and $1/\Gamma = 0.5$ ps, in both three-dimensional and contour plot representations. Contour levels indicate 0.005 steps from -0.01 to 0.04 , inclusive. (b) Spectra of $\Sigma_2(\omega; t_s)$ (solid lines) for several values of t_s , with $\delta\sigma_2(\omega; t_s)$ (dotted lines) shown for comparison. The spectrum for each t_s is denoted by color in the legend; with increasing t_s , σ_2 decreases uniformly as the carriers decay, while Σ_2 shows oscillations about $\Sigma_2 \approx 0$, with period $\Delta\nu = 1/t_s$ and an amplitude that decays with both ω and t_s . All spectra are normalized to $\Delta\sigma_0 \equiv \Delta ne^2\tau_s/m$.

domain oscillations shown in Figs. 2–4 depend only the sampling time t_s and are independent of the plasma frequency. More closely related oscillations appear in the pump-probe spectra of organic dyes and semiconductors when the pump-probe delay is less than the polarization dephasing time [22–25]. An important difference here, however, is that the dephasing time of these systems must always be less than the energy relaxation time, whereas the momentum relaxation time of a (super)conductor has no such bound.

As mentioned above, different phenomenological descriptions of a transient superconducting state are possible. For example, rather than generating a fully coherent superfluid component, one could imagine that the effect of the pump pulse is to suddenly increase the momentum relaxation time of the entire electron fluid to some large but still finite value.

The system would subsequently return to equilibrium through the decay of partial coherence and recovery of the normal state τ_s . We describe the TD-THz response for the case of a time-varying momentum relaxation rate in the Appendix, where we obtain the response function $\Sigma(\tau, t)$ in terms of $\gamma(t)$. Unlike the models considered above, we believe that the instantaneous conductivity $\sigma(\omega; t)$ is not well-defined in a system where γ depends explicitly on the time. Still, $\Sigma(\omega; t)$ remains a valid response function and can exhibit features that are similar to those predicted for the two-fluid model. In this case, the deviations from a Drude spectrum will be smaller than in the fully coherent superconductor, particularly if the maximum τ_s reached by the partially coherent state does not exceed the sampling time.

V. SUMMARY AND CONCLUSIONS

THz-TDS provides an elegant method for doing time-resolved photoconductivity measurements. In this paper we have focused on whether the response function $\Sigma(\omega; t_s)$ that is typically measured in time-resolved THz-TDS can be interpreted as the photoinduced change $\delta\sigma(\omega; t_s)$ in the instantaneous optical conductivity. Within a simple model, we have shown that $\Sigma(\omega; t_s)$ is never equivalent to $\delta\sigma(\omega; t_s)$, although we also found that $\Sigma(\omega; t_s)$ approaches $\delta\sigma(\omega; t_s)$ asymptotically in the limit $\gamma t_s \rightarrow \infty$, where γ is the Drude relaxation rate of the nonequilibrium carriers. In this limit, the current measured at t_s has an exponentially small dependence on the field applied at $t < 0$; that is, before the pump pulse arrives. In the opposite regime, $\gamma t_s \lesssim 1$, we presented an analytic expression that shows that $\Sigma(\omega; t_s)$ and $\delta\sigma(\omega; t_s)$ are entirely distinct response functions for the nonequilibrium Drude model. Here, the absence of nonequilibrium carriers for $t < 0$ creates a current imbalance for fields applied near $t = 0$ that persists until the measurement time. Nevertheless, we believe that even in this regime, information about the number density and the mobility of the photocarriers can be obtained by comparing $\Sigma(\omega; t_s)$ with theoretical models [12–16].

The effort to better understand the relationship of $\Sigma(\omega; t_s)$ to $\delta\sigma(\omega; t_s)$ was largely motivated by experiments reporting photoinduced transient superconductivity in cuprates and in K_3C_{60} . The evidence presented for superconductivity is that the instantaneous conductivity following photoexcitation in the normal state, $\sigma(\omega; t)$, has features characteristic of the equilibrium $\sigma(\omega)$ measured at $T \ll T_c$. To obtain the instantaneous conductivity it is assumed that $\sigma(\omega; t) = \sigma(\omega) + \Sigma(\omega; t)$, which is based on regarding $\Sigma(\omega; t)$ and $\delta\sigma(\omega; t)$ as equivalent. However, we have shown that these response functions are not equivalent and differ most strongly when carrier momentum relaxation rates become small. Superconductivity, in which the condensate momentum relaxation time diverges, is the most extreme example of the inequivalence of $\Sigma(\omega; t)$ and $\delta\sigma(\omega; t)$.

We considered two perspectives in attempting to model the response function $\Sigma(\omega; t)$ appropriate to photoinduced transient superconductivity. For a two-fluid model with a transient, fully coherent superfluid component, we predict strong oscillations along the frequency axis of $\Sigma(\omega; t)$, with a period inversely related to the sampling time. In the second perspective, the pump induces a partially coherent state, with an enhanced, but still finite, momentum relaxation time. In this

model, deviations from a Drude spectrum are again expected, though damped by the limited coherence time. In either case, the instantaneous conductivity $\sigma(\omega; t)$ is unobservable or ill-defined in the most physically interesting regimes, while time-resolved THz-TDS measures $\Sigma(\omega; t)$ directly. To advance research on photoinduced superconductivity and other collective states, we believe it important to distinguish them.

ACKNOWLEDGMENTS

J.S.D. thanks J. Bechhoefer for suggesting the equation of motion approach presented in the Appendix and acknowledges support from NSERC and CIFAR. J.O. acknowledges the Office of Basic Energy Sciences, Materials Sciences and Engineering Division, of the U.S. Department of Energy under Contract No. DE-AC02-05CH11231 for support.

APPENDIX: CLASSICAL DERIVATION OF THE NONEQUILIBRIUM RESPONSE

To extend the classical Drude model to photoexcited materials, we let both the carrier density n and the damping rate γ depend on time in the usual equation of motion. The current is then related to the field through the linear, first-order differential equation

$$\frac{dJ}{dt} + \left(\gamma - \frac{1}{n} \frac{dn}{dt} \right) J = \frac{ne^2}{m} E. \quad (\text{A1})$$

The extra damping term follows from the chain rule with $J = nev$ and causes the current to decay more rapidly when the carrier density decreases, as expected. Conversely, the damping term decreases when the carrier density increases, because our model incorrectly assumes that all carriers move with the same velocity [14]. Others have addressed this problem by expressing the current in terms of a distribution function, but their results reproduce Eq. (A1) in the usual case of carrier decay [12,14].

To solve Eq. (A1), we introduce the integrating factor

$$F(t, t_i) \equiv \frac{n(t_i)}{n(t)} \exp[\bar{\gamma}(t_i, t)(t - t_i)], \quad (\text{A2})$$

with

$$\bar{\gamma}(t_1, t_2) \equiv \frac{\int_{t_1}^{t_2} dt' \gamma(t')}{t_2 - t_1}, \quad (\text{A3})$$

the average damping rate over the interval (t_1, t_2) . Assuming $n \geq 0$ over (t_i, t) , we multiply Eq. (A1) by Eq. (A2) and integrate to get

$$J(t) - J(t_i) = \frac{n(t)e^2}{m} \int_{t_i}^t dt' \exp[-\bar{\gamma}(t', t)(t - t')] E(t'). \quad (\text{A4})$$

When n and γ are constant, Eq. (A4) gives the conventional Drude response. When n and γ vary with time, the current $J(t)$ includes contributions from impulses at earlier times t' , exponentially weighted by the average damping rate experienced over its history. An impulse with carrier density $n(t')$ will decay by the factor $n(t)/n(t')$ before it contributes to the current $J(t)$, so only the overall factor $n(t)$ appears outside the integral.

Referring now to Eq. (3), we let $n = n_{\text{eq}}$ and $\gamma = \gamma_{\text{eq}}$ at equilibrium, and use Eq. (A4) to find the current change $\delta J(t)$ following photoexcitation at $t = 0$:

$$\begin{aligned} \Sigma(\tau, t) = & \Theta(t)\Theta(t - \tau)\Theta(\tau) \frac{e^2}{m} \{ n(t) \exp[-\bar{\gamma}(t - \tau, t)\tau] \\ & - n_{\text{eq}} \exp(-\gamma_{\text{eq}}\tau) \}. \end{aligned} \quad (\text{A5})$$

For the specific case of a photoinduced carrier density $n(t) = n_{\text{eq}} + \Theta(t)\delta n(0)e^{-\Gamma t}$ with constant Drude scattering rate γ ,

$$\Sigma(\tau, t) = \Theta(t - \tau)\Theta(t) \frac{\delta n(0)e^2}{m} \exp(-\Gamma t)\Theta(\tau) \exp(-\gamma\tau). \quad (\text{A6})$$

The second factor of $\Theta(t)$ in Eq. (A6) is missing in Eq. (31) of Ref. [12], but this appears to be a typographical error, since the factor is necessary to obtain their Eq. (32). Otherwise, the expressions are equivalent.

-
- [1] R. Ulbricht, E. Hendry, J. Shan, T. Heinz, and M. Bonn, Carrier dynamics in semiconductors studied with time-resolved terahertz spectroscopy, *Rev. Mod. Phys.* **83**, 543 (2011).
 - [2] R. D. Averitt and A. J. Taylor, Ultrafast optical and far-infrared quasiparticle dynamics in correlated electron materials, *J. Phys.: Condens. Matter* **14**, R1357 (2002).
 - [3] D. N. Basov, R. D. Averitt, D. van der Marel, M. Dressel, and K. Haule, Electrodynamics of correlated electron materials, *Rev. Mod. Phys.* **83**, 471 (2011).
 - [4] J. Lloyd-Hughes and T.-I. Jeon, A review of the terahertz conductivity of bulk and nano-materials, *J. Infrared, Millimeter, Terahertz Waves* **33**, 871 (2012).
 - [5] D. Fausti, R. I. Tobey, N. Dean, S. Kaiser, A. Dienst, M. C. Hoffmann, S. Pyon, T. Takayama, H. Takagi, and A. Cavalleri, Light-induced superconductivity in a stripe-ordered cuprate, *Science* **331**, 189 (2011).
 - [6] W. Hu, S. Kaiser, D. Nicoletti, C. R. Hunt, I. Gierz, M. C. Hoffmann, M. Le Tacon, T. Loew, B. Keimer, and A. Cavalleri, Optically enhanced coherent transport in $\text{YBa}_2\text{Cu}_3\text{O}_{6.5}$ by ultrafast redistribution of interlayer coupling, *Nat. Mater.* **13**, 705 (2014).
 - [7] S. Kaiser, C. R. Hunt, D. Nicoletti, W. Hu, I. Gierz, H. Y. Liu, M. Le Tacon, T. Loew, D. Haug, B. Keimer, and A. Cavalleri, Optically induced coherent transport far above T_c in underdoped $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$, *Phys. Rev. B* **89**, 184516 (2014).
 - [8] M. Mitrano, A. Cantaluppi, D. Nicoletti, S. Kaiser, A. Perucchi, S. Lupi, P. Di Pietro, D. Pontiroli, M. Riccò, A. Subedi, S. R. Clark, D. Jaksch, and A. Cavalleri, An optically stimulated superconducting-like phase in K_3C_60 far above equilibrium T_c , *arXiv:1505.04529*.
 - [9] R. D. Averitt, G. Rodriguez, J. L. W. Siders, S. A. Trugman, and A. J. Taylor, Conductivity artifacts in optical-pump THz-

- probe measurements of $\text{YBa}_2\text{Cu}_3\text{O}_7$, *J. Opt. Soc. Am. B* **17**, 327 (2000).
- [10] H. Němec, F. Kadlec, and P. Kužel, Methodology of an optical pump-terahertz probe experiment: An analytical frequency-domain approach, *J. Chem. Phys.* **117**, 8454 (2002).
 - [11] E. Hendry, M. Koeberg, J. M. Schins, H. K. Nienhuys, V. Sundström, L. D. A. Siebbeles, and M. Bonn, Interchain effects in the ultrafast photophysics of a semiconducting polymer: THz time-domain spectroscopy of thin films and isolated chains in solution, *Phys. Rev. B* **71**, 125201 (2005).
 - [12] H. Němec, F. Kadlec, S. Surendran, P. Kužel, and P. Jungwirth, Ultrafast far-infrared dynamics probed by terahertz pulses: A frequency domain approach. I. Model systems, *J. Chem. Phys.* **122**, 104503 (2005).
 - [13] H. Němec, F. Kadlec, C. Kadlec, P. Kužel, and P. Jungwirth, Ultrafast far-infrared dynamics probed by terahertz pulses: A frequency-domain approach. II. Applications, *J. Chem. Phys.* **122**, 104504 (2005).
 - [14] H.-K. Nienhuys and V. Sundström, Intrinsic complications in the analysis of optical-pump, terahertz probe experiments, *Phys. Rev. B* **71**, 235110 (2005).
 - [15] J. M. Schins, E. Hendry, M. Bonn, and H. G. Muller, Retrieving the susceptibility from time-resolved terahertz experiments, *J. Chem. Phys.* **127**, 094308 (2007).
 - [16] J. M. Schins, Interpretation of ultrafast pump-probe terahertz experiments in the time domain: How to exploit two-dimensional correlations, *Phys. Rev. B* **83**, 205111 (2011).
 - [17] J. T. Kindt and C. A. Schmuttenmaer, Theory for determination of the low-frequency time-dependent response function in liquids using time-resolved terahertz pulse spectroscopy, *J. Chem. Phys.* **110**, 8589 (1999).
 - [18] G. Gallot and D. Grischkowsky, Electro-optic detection of terahertz radiation, *J. Opt. Soc. Am. B* **16**, 1204 (1999).
 - [19] G. Gallot, J. Zhang, R. W. McGowan, T.-I. Jeon, and D. Grischkowsky, Measurements of the THz absorption and dispersion of ZnTe and their relevance to the electro-optic detection of THz radiation, *Appl. Phys. Lett.* **74**, 3450 (1999).
 - [20] M. Schall, M. Walther, and P. U. Jepsen, Fundamental and second-order phonon processes in CdTe and ZnTe, *Phys. Rev. B* **64**, 094301 (2001).
 - [21] M. C. Beard, G. M. Turner, and C. A. Schmuttenmaer, Transient photoconductivity in GaAs as measured by time-resolved terahertz spectroscopy, *Phys. Rev. B* **62**, 15764 (2000).
 - [22] C. H. Brito Cruz, R. L. Fork, W. H. Knox, and C. V. Shank, Spectral hole burning in large molecules probed with 10 fs optical pulses, *Chem. Phys. Lett.* **132**, 341 (1986).
 - [23] C. H. Brito Cruz, J. P. Gordon, P. C. Becker, R. L. Fork, and C. V. Shank, Dynamics of spectral hole burning, *IEEE J. Quantum Electron.* **24**, 261 (1988).
 - [24] B. Fluegel, N. Peyghambarian, G. Olbright, M. Lindberg, S. W. Koch, M. Joffre, D. Hulin, A. Migus, and A. Antonetti, Femtosecond Studies of Coherent Transients in Semiconductors, *Phys. Rev. Lett.* **59**, 2588 (1987).
 - [25] M. Joffre, D. Hulin, A. Migus, A. Antonetti, C. Benoit à la Guillaume, N. Peyghambarian, M. Lindberg, and S. W. Koch, Coherent effects in pump-probe spectroscopy of excitons, *Opt. Lett.* **13**, 276 (1988).